

# 1.4123 (X40CrMoVN16-2)

## Material Designation

1.4123                   DIN  
 S42025                 UNS  
 S42000/Type 420 Mod   ASTM

## Standards

DIN EN 10088-3  
 SAE AMS 5925 (chemical composition)  
 ASTM F899

## Chemical Composition Mass-%

	C	Si	Mn	P	S	Cr	Mo	Ni	V	N
min.	0,37	-	-	-	-	15,0	1,50	-	0,20	0,16
max.	0,45	0,60	0,60	0,020	0,005	16,0	1,90	0,3	0,40	0,25

Customer specific restrictions upon request

## Properties

1.4123 is a nitrogen-alloyed, hardenable stainless martensitic steel with good corrosion resistance.

The ESR-variant fulfills highest requirements towards homogeneity and cleanliness and offers outstanding grindability and polishability.

## Delivery Condition

- ✂ annealed (+A) max. 255 HBW
- ✂ quenched and tempered (+QT) upon request

## Application Area


High demands on wear and corrosion resistance as well as on cutting edge retention. High surface qualities.

## Typical Applications

- ✂ Surgical instruments
- ✂ Fuel injections systems
- ✂ Cutting tools
- ✂ Ball and roller bearings

## Heat Treatment Guideline Values

	Temperature [°C]	Cooling medium
Annealing (+A)	800 - 880	Furnace, Air
Quenching and tempering (+QT)	950 - 1050 (Hardening)	Oil, subzero treatment for hardening temperatures > 1020 °C (Risk for denitridation / nitridation)
	180 - 550 (Tempering)	Air

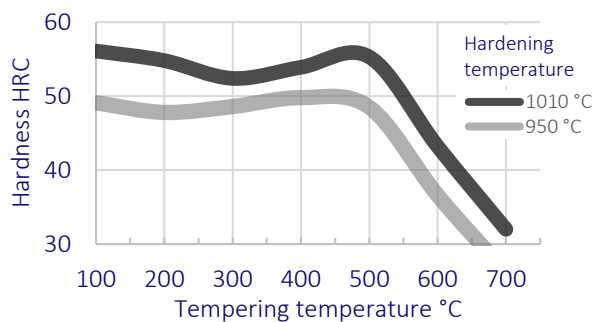

## Quality

- ISO 9001
- ISO 14001
- ISO 50001
- Approvals acc. to standards like ABS, BV, DNVGL ...
- Customer specific approval certificates

## Innovation

- Fully automated ultrasonic testing up to dia. 1000 mm
- CO<sub>2</sub>-reduction by innovative heat treatment solutions

## Flexibility

- Product range from fine wire to forging
- Directly from stock close at hand

## Individuality

- Dimensions
- Tolerances
- Surface qualities
- Delivery conditions

## Your personal contact:

### BGH Edelstahlwerke GmbH

Am Stahlwerk 1  
 01705 Freital  
 +49 351 646-0  
 info@bgh.de  
 www.bgh.de

